

ESL-TR-91-52

**MATERIALS FOR AIR-MOBILE  
STRUCTURES**

**M.A. ROCHEFORT, L.C. MUSZYNSKI**

**APPLIED RESEARCH ASSOCIATES, INC.  
POST OFFICE BOX 40128  
TYNDALL AFB FL 32403**

**DECEMBER 1995**

**FINAL REPORT**

**NOVEMBER 1989 - OCTOBER 1991**

**APPROVED FOR PUBLIC RELEASE:  
DISTRIBUTION UNLIMITED**

19960802 026



**ENGINEERING RESEARCH DIVISION  
Air Force Civil Engineering Support Agency  
Civil Engineering Laboratory  
Tyndall Air Force Base, Florida 32403**



## NOTICE

The following commercial products (requiring Trademark<sup>R</sup>) are mentioned in this report. Because of the frequency of usage, the Trademark was not indicated. If it becomes necessary to reproduce any segment of this document containing any of these names, this notice must be included as part of that reproduction.

AVCO 5505/4 - BORON  
AVCO 5521/4 - BORON  
Bridon SM  
Cycom 1010  
Cycom 1827 GT 6150  
Cycom 3100 + T300  
Cycom 985-1 GF 6135H5  
Cycom 985-1 GT-2148  
Dion FR 6131  
E 21718 x 61  
E 260H  
E 261H  
EMI Shielding Gr AC 30-60  
EMI Shielding Gr LS AC 40-60  
ETR-FR-C-P  
Extren 625  
Filon Standard  
Fire Snuf 25A 1230  
Fire Snuf 25A 820  
Flomat 5580  
Fortafil 3(C)  
FM 73  
FX 91C34  
Gillfab 1086  
Hexcel F584/T4A145  
Hexcel F584/T5A145  
Hexcel F584/T5A190  
Hexcel F584/T8A145  
HST-II-P  
Kevlar  
Lamitex G215  
Lamitex Grade G-5

Lamitex Grade G-9  
Lamitex T6G91  
Lytex 4105  
Metlbond 1137-1  
N-S Pultruded Composites  
Nomex  
NY-30GF  
NY-40GF  
Polycor C-106  
Polypenco Ultem 1000  
Polystruc M-106  
Polytron E-106  
Polytron E-206  
Premi-Glas  
Pultruded Bar Stock  
RTP 287 TFE 10  
Ryertex G-10  
Ryertex G-11  
S-2 Glass  
Scotch-Weld 2216 B/A  
Silryn S-106  
Silryn S-206  
Spectra  
Thornel 2500  
Tred-Safe  
VE 49595  
Vespel SP-1 "S"  
Vespel SP-21 "S"  
Vespel SP-22 "S"  
8057  
8068

Mention of the products listed above does not constitute Air Force endorsement or rejection of this product, and use of the information contained herein for advertising purposes without obtaining clearance according to existing contractual agreements is prohibited.

Please do not request copies of this report from HQ AFCESA/RA. Additional copies may be purchased from: National Technical Information Service; 5285 Port Royal Road; Springfield, VA 22161.

Federal Government Agencies and their contractors registered with Defense Technical Information Center should direct requests for copies of this report to: Defense Technical Information Center; Cameron Station; Alexandria, VA 22314.

## REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

1a. REPORT SECURITY CLASSIFICATION UNCLASSIFIED			1b. RESTRICTIVE MARKINGS		
2a. SECURITY CLASSIFICATION AUTHORITY			3. DISTRIBUTION / AVAILABILITY OF REPORT Approved for public release. Distribution Unlimited.		
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE					
4. PERFORMING ORGANIZATION REPORT NUMBER(S)			5. MONITORING ORGANIZATION REPORT NUMBER(S) ESL-TR-91-52		
6a. NAME OF PERFORMING ORGANIZATION Applied Research Associates, Inc.	6b. OFFICE SYMBOL (If applicable) ARA	7a. NAME OF MONITORING ORGANIZATION Air Force Civil Engineering Support Agency			
6c. ADDRESS (City, State, and ZIP Code) P.O. Box 40128 Tyndall AFB, FL 32403		7b. ADDRESS (City, State, and ZIP Code) HQ AFCEA/RACS Tyndall AFB, FL 32403			
8a. NAME OF FUNDING / SPONSORING ORGANIZATION HQ AFCEA	8b. OFFICE SYMBOL (If applicable) RACS	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER F08635-88-C-0067			
8c. ADDRESS (City, State, and ZIP Code) Tyndall AFB, FL 32403		10. SOURCE OF FUNDING NUMBERS			
		PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification) Materials for Air-Mobile Structures					
12. PERSONAL AUTHOR(S) Rocheft, M.A., Muszynski, L.C.					
13a. TYPE OF REPORT Final	13b. TIME COVERED FROM Nov 89 TO Oct 91	14. DATE OF REPORT (Year, Month, Day) December 1995		15. PAGE COUNT 47	
16. SUPPLEMENTARY NOTATION Availability of this report is specified on reverse of front cover.					
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)			
FIELD	GROUP	SUB-GROUP	Shelter Construction Materials Cores		
			Composites Ballistic Materials		
			Adhesives		
19. ABSTRACT (Continue on reverse if necessary and identify by block number) The objective of this research effort was to identify and catalog the engineering properties of commercially available, advanced composite materials with potential for use in lightweight shelter construction. A number of commercially available, potentially air-mobile, protective shelter construction materials were identified and divided into four main categories: Composites, Cores, Adhesives, and Ballistic Materials. The best materials in each category were described and a brief summary of each materials engineering properties was presented. The manufacturer of every material was identified.					
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION UNCLASSIFIED		
22a. NAME OF RESPONSIBLE INDIVIDUAL William S. Strickland			22b. TELEPHONE (Include Area Code) (904)283-2918	22c. OFFICE SYMBOL RACS	

## EXECUTIVE SUMMARY

### A. OBJECTIVE

The objective of this research effort was to identify and catalog the engineering properties of commercially available, advanced composite materials with potential for use in lightweight shelter construction.

### B. BACKGROUND

Transportable shelters play an important role in the mission of the United States Air Force. Portable shelters are used for the expedient beddown of personnel during crises and mobility forces during deployment. They are also used as temporary structures in place of those vital air base facilities damaged by war or other disaster.

Current shelters are bulky, hard to erect and maintain, and provide only limited environmental protection. In addition, they provide little, if any, protection against small arms fire, much less the blast and fragmentation associated with indirect fire weapons and aerial munitions.

Based on the deficiencies of current shelters, the Air Force has expressed a need for an improved set of portable protective shelters.

### C. SCOPE

It is hypothesized that the most promising approach to developing a new series of lightweight, air-mobile shelters involves coupling the use of modern aerospace composites with an innovative structural geometry. By designing structures in such a way as to exploit the strengths of current advanced composites, it may be possible to develop a family of lightweight shelters possessing significant structural hardness.

This report documents the materials survey phase of the improved air-mobile shelter design project. The scope of this phase was to identify and catalog the engineering properties of commercially available materials with potential for use in lightweight shelter construction. This shelter materials catalog was developed by searching existing literature. No laboratory testing was performed.

### D. EVALUATION METHODOLOGY

Materials were selected based on their strength, weight and ballistic resistance. These properties were considered to be the most critical for air-mobile shelter design.

### E. TEST DESCRIPTION

(N/A)

## F. RESULTS

A number of commercially available, potentially air-mobile, protective shelter construction materials were identified and divided into four main categories: Composites, Cores, Adhesives, and Ballistic Materials. The best materials in each category were described, and a brief summary of each material's engineering properties was presented. The manufacturer of every material was identified.

## G. CONCLUSIONS

Modern materials offer the opportunity to quickly improve present shelter designs, as well as develop new shelter concepts.

Better core and facing materials offer a quick improvement to current tactical shelter designs. In fact, future Army tactical shelters are being developed with composite materials in mind. The aluminum skins employed by current shelters will be replaced by graphite/epoxy panels. The graphite/epoxy skins will reduce shelter weight, improve ballistic protection, and increase electromagnetic shielding.

## H. RECOMMENDATIONS

Future air-mobile shelter designs should exploit the impressive properties of modern engineering materials. The best shelter concepts will most likely involve a combination of materials, coupled with an innovative structural geometry. The geometry should exploit the strengths of each particular material.


## PREFACE


This report was prepared by Applied Research Associates, Inc., P.O. Box 40128, Tyndall Air Force Base, FL 32403, under Scientific and Engineering Technical Assistance (SETA) contract F08635-88-C-0067 with the Air Force Civil Engineering Support Agency, Engineering Research Division (AFCEA/RAC), Tyndall Air Force Base, FL 32403. The work was performed between November 1989 and October 1991 as part of SETA Subtask 4.02, "Composite Materials for Structures".


Mr. Charles E. Bailey was the Air Force Project Monitor from November 1989 through August 1991. From September 1991 through its completion, the project was monitored by Mr. Walter C. Buchholtz.


This report has been reviewed by the Public Affairs Office and is releasable to the National Technical Information Service (NTIS). At NTIS, it will be available to the general public, including foreign nations.

This technical report has been reviewed and is approved for publication.

  
WALTER C. BUCHHOLTZ, GS-13  
Project Monitor, Airbase  
Survivability Branch

  
NEIL H. FRAVEL, Lt Col, USAF  
Chief, Engineering Research  
Division

  
WILLIAM S. STRICKLAND, GM-14  
Chief, Airbase Survivability  
Branch

  
FRANK P. GALLAGHER, Col, USAF  
Director, Civil Engineering  
Laboratory

## TABLE OF CONTENTS

Section	Title	Page
I	INTRODUCTION.....	1
	A. OBJECTIVE.....	1
	B. BACKGROUND.....	1
	C. SHELTER DESIGN.....	1
	D. SCOPE OF REPORT.....	2
II	LITERATURE REVIEW & TECHNICAL APPROACH.....	3
	A. INTRODUCTION.....	3
	B. REVIEW OF SELECTED ADVANCED MATERIALS REFERENCES.....	3
	C. PREVIOUS SHELTER MATERIAL SURVEYS.....	5
	D. GATHERING MATERIAL PROPERTY DATA.....	6
	1. Following a Lead.....	6
	2. A Lesson Learned.....	6
	3. Technical Approach.....	6
III	MATERIALS FOR AIR-MOBILE STRUCTURES.....	7
	A. INTRODUCTION.....	7
	B. COMPOSITES.....	8
	1. Advanced Composites.....	9
	2. Compounds.....	10
	3. Laminates.....	12
	4. Panels and Sheets.....	12
	5. Prepregs.....	13
	6. Profiles and Shapes.....	14
	C. CORES.....	14
	D. ADHESIVES.....	19
	1. Factory Bonding.....	19
	2. Field Bonding.....	20
	E. BALLISTIC MATERIALS.....	20
IV	SUMMARY AND CONCLUSIONS.....	22
	A. SUMMARY.....	22
	B. CONCLUSIONS.....	22
	1. Present Shelters.....	22
	2. Future Designs.....	22
V	REFERENCES.....	23

TABLE OF CONTENTS  
(Continued)

Section	Title	Page
VI	BIBLIOGRAPHY.....	26
APPENDIX		
A	MATERIAL PROPERTIES OF SELECTED COMPOSITES.....	29
B	PROPERTIES OF HEXAGONAL 2024 ALUMINUM HONEYCOMB.....	45



## LIST OF FIGURES

Figure	Title	Page
1	Specific Tensile Strength versus Specific Tensile Modulus for Various Commercially Available 65 Vol% Unidirectional Epoxy- Matrix Composites and for Steel and Aluminum.....	8
2	Hexagonal Honeycomb Geometry.....	15
3	Typical Honeycomb Stabilized Compression Strength vs. Density.....	16
4	Typical Honeycomb "L" Shear Strength vs. Density.....	17
5	Typical Honeycomb "W" Shear Strength vs. Density.....	17
6	Typical Honeycomb "L" Shear Modulus vs. Density.....	18
7	Typical Honeycomb "W" Shear Modulus vs. Density.....	18

## LIST OF TABLES

Table	Title	Page
1	STRONGEST ADVANCED COMPOSITES.....	9
2	STRONGEST COMPOUNDS.....	11
3	STRONGEST BULK MOLDING COMPOUNDS.....	11
4	STRONGEST SHEET MOLDING COMPOUNDS.....	12
5	STRONGEST LAMINATES.....	12
6	STRONGEST PANELS.....	13
7	STRONGEST SHEETS.....	13
8	STRONGEST PREPREGS.....	14
9	STRONGEST PROFILES AND SHAPES.....	14
10	COMPARISON OF BALLISTIC FIBERS FOR HARD ARMOR.....	21
A-1	ADVANCED COMPOSITES - MATERIAL PROPERTIES.....	30
A-2	COMPOUNDS - MATERIAL PROPERTIES.....	32
A-3	BULK MOLDING COMPOUND - MATERIAL PROPERTIES.....	33
A-4	SHEET MOLDING COMPOUNDS - MATERIAL PROPERTIES.....	34
A-5	LAMINATES - MATERIAL PROPERTIES.....	36
A-6	PANELS - MATERIAL PROPERTIES.....	38
A-7	SHEETS - MATERIAL PROPERTIES.....	39
A-8	PREPREGS - MATERIAL PROPERTIES.....	41
A-9	PROFILES AND SHAPES - MATERIAL PROPERTIES.....	43
B-1	PROPERTIES OF HEXAGONAL 2024 ALUMINUM HONEYCOMB.....	46

## SECTION I

### INTRODUCTION

#### A. OBJECTIVE

In response to TAF SON 314-88, the Engineering Research Division of the Air Force Civil Engineering Support Agency (HQ AFCESA/RAC) has initiated a multi-year research project to develop an improved set of air-mobile protective shelters.

#### B. BACKGROUND

Transportable shelters play an important role in the mission of the United States Air Force. Portable shelters are used for the expedient beddown of personnel during crises and mobility forces during deployment. They are also used as temporary structures in place of those vital air base facilities damaged by war or other disaster.

The Air Force utilizes three portable shelter deployment packages. They are referred to as Harvest Eagle, Harvest Bare, and Harvest Falcon. The Harvest Eagle soft wall shelters (i.e., tents) developed in 1957-65 and the Harvest Bare hard wall shelters developed in 1965-72 represent the mainstay capability of the Air Force to rapidly deploy and operate from forward locations. The Harvest Falcon bare base infrastructure centers on an enhanced version of a softwall shelter, the Tent Extendable Modular Personnel (TEMPER) tent. With the exception of the TEMPER tent, all existing transportable shelters utilize old technology. The current shelters are bulky, hard to erect and maintain, and provide only limited environmental protection. In addition, they provide little, if any, protection against small arms fire, much less the blast and fragmentation associated with indirect fire weapons and aerial munitions.

Based on the deficiencies of current shelters, the Air Force has expressed a need for an improved set of portable protective shelters. TAF SON 314-88, Statement of Operational Need for New Family of Portable Shelters, documents an immediate need for a family of air-mobile, easily erectable, maintainable, semi-hardened shelters.

#### C. SHELTER DESIGN

The design of any structure involves an interaction between structural analysis/design and materials selection/development. The design of protective shelters is considerably more complicated than that of a conventional structure.

Shelter design begins with the definition of the threat. The threat, or the attack which the shelter must withstand, is dependent on the mission of the structure being designed.

Once the threat has been specified, it must be translated into a series of free-field conventional weapon effects. Shelters may be subjected to a combination of airblast, fragmentation, penetration, ground shock, and cratering effects. Important weapon effects will depend on whether the structure will be aboveground or buried.

At this point in the design phase, it is necessary to specify the structural geometry and material properties. The geometry and material properties are used to calculate the structural properties (e.g., strength, stiffness, weight) of the key members.

Initial structural properties are used to construct a computer model of the shelter. The model is analyzed as it is being subjected to the appropriate weapon effect loadings. The stresses in and deflections of all key members are calculated. If the stresses and deflections of all members are within prescribed design limits, then the initial design is valid. This is usually not the case.

If the initial design is not satisfactory, there are two alternatives. The first alternative is to select/design new materials for the shelter. The second alternative is to change the geometry of the shelter. Member loadings can be changed dramatically by changing the configuration of the shelter.

A new structural model incorporating the revised combination of material properties and/or structural geometry is then analyzed. This process continues until a satisfactory structural response is calculated.

The shelter design process involves a combination of structural and materials engineering. If the design utilizes advanced composite materials, cooperation between structural and materials engineers becomes critical. Since most protective structures have been constructed of reinforced concrete, very few protective structural designers are familiar with the properties of aerospace composites. The materials engineer must therefore play a more active role in the design process of protective structures.

#### D. SCOPE OF REPORT

It is hypothesized that the most promising approach to developing a new series of lightweight, air-mobile shelters involves coupling the use of modern aerospace composites with an innovative structural geometry. By designing structures in such a way as to exploit the strengths of current advanced composites, it may be possible to develop a family of lightweight shelters possessing significant structural hardness.

This report documents the materials survey phase of the improved air-mobile shelter design project. The objective of this phase was to identify and catalog the engineering properties of commercially available, advanced composite materials with potential for use in lightweight shelter construction. This shelter materials catalog was developed by searching existing literature. No laboratory testing was performed.

## SECTION II

### LITERATURE REVIEW & TECHNICAL APPROACH

#### A. INTRODUCTION

A literature search of available information pertaining to composite materials and transportable shelters, was conducted through the Air Force Civil Engineering Support Agency's Technical Information Center (AFCEA/TIC).

A substantial number of recent books, reports, journals, and conferences dealing with composite materials exist, making it impossible to obtain and review all the references uncovered; therefore, a representative sample was selected for review. A list of the references requested is included in the Bibliography under the heading, "Properties and Mechanics of Advanced Composite Materials." These 23 references provide a realistic picture of the quantity and quality of information currently available on advanced composite structural materials. Some of the references focus on the engineering properties of composites, while others concentrate on the application of composites in design. Both types are useful to the design engineer. For the reader interested in searching additional references, the Engineers' Guide to Composite Materials [1] contains a bibliography of 78 reference books and 13 technical journals dealing with composite materials. Reference 1 also includes an excellent glossary of terms relating to composites.

Eight reports pertaining to transportable shelter research were also requested and reviewed. A list of these reports is given in the Bibliography under the heading, "Transportable Shelter Research." These references provide insight into recent Army and Air Force portable shelter research.

#### B. REVIEW OF SELECTED ADVANCED MATERIALS REFERENCES

Structural and mechanical engineers are beginning to routinely utilize advanced materials (e.g., composites, plastics, ceramics, adhesives, etc.) in their designs. The widespread application of these new materials in engineering design has created a need for accessible material property information. This need has resulted in the recent appearance of a multitude of engineering references pertaining to advanced, high-strength, lightweight materials. The remainder of this section is devoted to a brief review of several excellent reference books published since the mid-1980s.

In addition to an extensive discussion of the recreational, automotive, aerospace, marine, medical, electronic, and structural applications of composite materials, the Engineers' Guide to Composite Materials [1] contains more than 200 pages of property data for reinforcements, polymer matrix composites, metal matrix composites, and ceramic and glass matrix composites. As mentioned previously, this reference also contains an excellent bibliography and glossary of terms.

Another source of information on composite materials is a four-volume reference series, called the Handbook of Composites [2-5]. Volume 1: Strong Fibres [2] contains more than 700 pages of technical information pertaining to inorganic, carbon, and organic, high-modulus fibres. Volume 2: Structures and

Design [3] includes a survey of analysis techniques, design considerations, and design methods for fibrous composite structures. Volume 3: Failure Mechanics of Composites [4] describes the various failure mechanisms and the testing of composite materials. Volume 4: Fabrication of Composites [5] discusses the fabrication of composite materials, ranging from fiber-reinforced ceramics to biological composites.

The four-volume Engineered Materials Handbook [6-9] is another excellent materials reference series. Volume 1: Composites [6] contains more than 900 pages of information (161 articles) pertaining to properties, testing, analysis and design, manufacturing, failure analysis, and applications of advanced composite materials. Volume 2: Engineering Plastics [7] presents over 800 pages of similar information relevant to engineering plastics. Volume 3: Adhesives and Sealants [8] includes 97 articles comprising one of the most thorough reviews of the selection, design, properties, and uses of structural adhesives and sealants ever published. Volume 4: Ceramics and Glasses [9] contains 1100 pages of practical information on processing, properties, testing and characterization, design, and applications of various types of ceramics and glasses.

The most complete and concise set of engineering material property data for advanced, nonmetallic materials has been assembled by D.A.T.A., Inc. This reference series [10-12], called the "desk-top data bank," contains thousands of pages of material property information for composites, plastics, and adhesives. In addition, D.A.T.A. Inc.'s 2000-page reference on plastics is available as a computerized database [13].

The reference book, Composites & Laminates [10], is the broadest single source of data on engineering properties of modern composite materials. This reference contains data for over 3000 materials from more than 130 manufacturers. Up to 20 material properties are listed for each material. The 3000 materials are grouped into eight categories (Composites and Advanced Composites, Compounds, Films, Laminates, Panels, Prepregs, Profiles and Shapes, and Sheets), and ranked according to 12 material properties (Compressive Strength, Deflection Temperature at 264 psi, Density, Dielectric Strength, Elongation at Break, Flexural Modulus, Flexural Strength at Break, Izod Notched at RT, Linear Shrinkage, Tensile Modulus, Tensile Strength at Break, and Water Absorption).

The INTERNATIONAL PLASTICS SELECTOR [13] is the self-proclaimed "world's most extensive database of Plastics Materials." It is a computerized database of engineering information for over 12,700 plastic materials from more than 200 manufacturers. Plastics can be searched and sorted according to 50 physical, mechanical, electrical, thermal, and flammability properties. This database is updated quarterly to keep abreast of daily material changes. As an illustration of the rapid change occurring in the plastics industry, INTERNATIONAL PLASTICS SELECTOR sales literature states that, "1,613 new plastics materials were introduced, and 703 materials were discontinued between July 1989 and October 1989."

A subset of the engineering data contained in the INTERNATIONAL PLASTICS SELECTOR is contained in the reference, Plastics [11]. This reference lists physical, mechanical, thermal, and electrical properties for over 9000 commercially available plastics from more than 180 manufacturers. The 9000

plastics have been grouped into 61 generic categories (e.g., Acrylic, Epoxy, Nylon, Silicone, etc.), then ranked according to 22 material properties (Processing Temperature, Linear Mold Shrinkage, Melting Point, Density, Tensile Strength at Yield, Tensile Strength at Break, Percent Elongation at Break, Tensile Modulus, Flexural Strength at Yield, Flexural Modulus, Compressive Strength, Izod Notched at R.T., Hardness, Thermal Conductivity, Linear Thermal Expansion, Deflection Temperature at 264 psi, Deflection Temperature at 66 psi, Voltage Resistivity, Dielectric Strength, Dielectric Constant at  $10^6$  HZ, Dissipation Factor at  $10^6$  HZ, and Percent Water Absorption at 24 hours).

The reference book, Adhesives [12], concisely lists the physical, mechanical, and thermal properties of more than 3000 commercially available adhesives, sealants, and primers from more than 100 manufacturers. The adhesives are grouped into 12 classes, and ranked according to seven material properties (Flash Point, Glass Transition Temperature, Lap Shear Range - Low, Lap Shear Range - High, Service Temp Range - Low, Service Temp Range - High, and Viscosity).

### C. PREVIOUS SHELTER MATERIAL SURVEYS

The concept of a catalog of engineering properties for potential shelter construction materials is not new.

In 1985, Mr. D. Robert Askins of the University of Dayton Research Institute suggested the creation of a shelter Materials Advisory Document (MAD) [14]. According to Mr. Askins, "The goal of this document will be to provide a focal point for gathering and disseminating information on materials available for use in the construction, repair, testing, and inspection of tactical shelters." Mr. Askins proposed a tentative list of shelter-related materials which should be included in the MAD. The list included: adhesives, cores, skins, fasteners, primers, paints, sealants, armor, gaskets, weather seals, potting compounds, core splice materials, repair materials, composites, foams, and metal hardware. He went on to give example data for typical adhesive and core materials.

In 1986, the Air Force Wright Aeronautical Laboratory published the results of a state-of-the-art survey of materials for developing a Transportable Collective Protection System (TCPS) [15]. This materials survey was conducted by Haug, Garic and Pharr, of Computer Sciences Corporation (CSC). Their approach was to solicit information directly from material manufacturers. They contacted more than 400 vendors of engineering materials. After analyzing all the information received, they grouped the materials into five categories: metals, plastics, composites, fabrics, and core materials. A fundamental assumption of the CSC survey was that engineering properties should be collected only for "finished" materials readily available from current manufacturers. Therefore, information on additive compounds, resins, fillers, and reinforcements was not included in the survey, since they are not structural materials or finished products in and of themselves.

Reference 15 concluded with opinions regarding the most appropriate combination of materials for shelter construction. In summary, Haug, Garic and Pharr felt that no single, homogeneous material inherently possesses the performance characteristics required to serve effectively in the TCPS applica-



tion. A satisfactory material could be achieved by combining various optimum materials from suitable material categories into a composite, a multilayered fabric, or a laminate. Laminated materials constructed from various combinations of the top-rated metals, plastics, and fabrics, together with the top-rated core material will likely provide the optimum overall properties.

#### D. GATHERING MATERIAL PROPERTY DATA

##### 1. Following a Lead

Since Mr. Askins' proposed MAD [14] was very similar in objective to this project, the authors telephoned Mr. Askins to determine the current status of the MAD. Mr. Askins stated that the MAD project had been discontinued before it ever really started. The members of the tactical shelter design community could not decide which properties, of what materials, should be included in the MAD. Since the scope of the MAD was never properly defined, the effort was discontinued.

##### 2. A Lesson Learned

The materials survey conducted by Haug, Garic, and Pharr [15] illustrates the difficulty in soliciting materials information directly from manufacturers. Despite contacting more than 400 manufacturers, their efforts resulted in "complete" engineering data for only 81 materials: 13 metals, 31 plastics, 12 composites, 17 fabrics, and 8 cores.

##### 3. Technical Approach

Engineering properties of materials can be obtained from many sources, including: reference books, technical journals and reports, conference proceedings, computerized databases, and manufacturers' literature.

Technical journals, reports, and conference proceedings are most useful for obtaining detailed information about a particular material. They are not, however, an appropriate source for gathering information pertaining to an entire class of materials. Attempting to extract a broad range of engineering data from these sources would take a prohibitive amount of time.

Reference 15 illustrates the difficulty of obtaining information directly from material manufacturers.

To gather as much information as possible, in a limited time, the information-gathering process should begin with reference books (e.g., References 1-12) and computerized databases (e.g., Reference 13). Once a solid core of information has been gathered from these sources, it can be supplemented with data obtained from technical reports and manufacturers' literature.



### SECTION III

## MATERIALS FOR AIR-MOBILE STRUCTURES

### A. INTRODUCTION

The two most important shelter design constraints are shelter size, and the combined dead and live loads which must be supported (i.e., resisted). The dead loads consist of the self-weight of the structure, plus the weight of any ballistic armor or insitu covering material (e.g., soil or rock rubble). The live loads are loads imposed on the structure due to conventional weapon attack. Airblast, fragmentation, ground shock, and ballistic impact are the primary live loads which must be resisted. Air-mobile shelters are subject to an additional design constraint, air-transportability. Weight and packing volume limitations are the main restrictions imposed by this constraint. Due to their high strength and low weight, modern composite materials are an obvious choice for air-mobile shelter construction. Many advanced composites have strength-to-weight ratios several times greater than those of the best metals. Figure 1 [16] is a plot of specific tensile strength (strength/density) versus specific tensile modulus (modulus/density) for several commercially available, unidirectional composites and for steel and aluminum. The composite strengths and moduli were calculated from fiber properties, using the "rule of mixtures."

Knowing the tensile strength (or modulus) of the reinforcing fibers and the matrix material, the tensile strength (or modulus) of a unidirectional composite in the fiber direction can be estimated using the rule of mixtures. According to the rule of mixtures, the composite tensile strength is estimated as

$$T_c = T_f V_f + T_m V_m \quad (1)$$

where,  $T_f$  is the tensile strength of the fibers,  $V_f$  is the fiber volume fraction,  $T_m$  is the tensile strength of the matrix material,  $V_m$  is the matrix volume fraction, and  $T_c$  is the tensile strength of the composite. To estimate composite moduli in the fiber direction, the rule of mixtures is expressed as

$$E_c = E_f V_f + E_m V_m \quad (2)$$

where,  $E_f$ ,  $E_m$ , and  $E_c$  are the fiber, matrix, and composite moduli, respectively.

By varying the type and volume fraction of fibers, composite fabricators can produce unidirectional composites with a wide range of tensile strengths and stiffnesses. Thousands of composite materials are commercially available. These materials are used in applications ranging from sporting goods (e.g., tennis rackets, golf clubs, skis, etc.) to space vehicles. The goal of this study was to determine which of these commercially available materials have the greatest potential for air-mobile shelter construction.

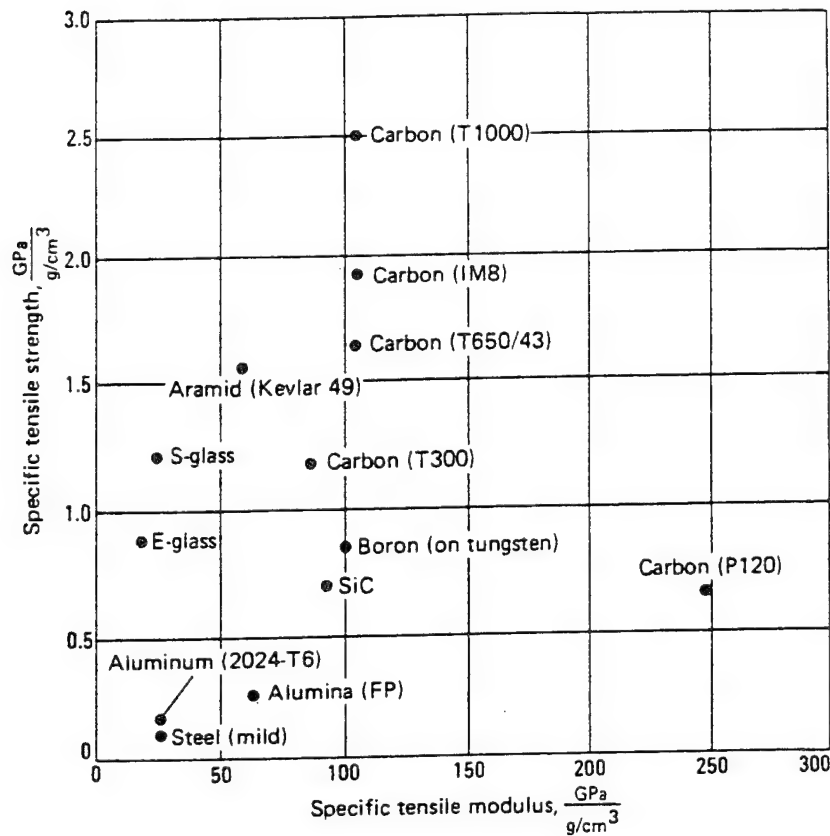


Figure 1. Specific Tensile Strength versus Specific Tensile Modulus for Various Commercially Available 65 Vol% Unidirectional Epoxy-Matrix Composites and for Steel and Aluminum. Note that T1000 Carbon Fiber is Available only in Limited Quantities [16].

Based on current tactical shelter research and available composites literature, several materials have been identified as candidates for air-mobile shelter construction. The materials have been grouped into four main categories: Composites, Cores, Adhesives, and Ballistic Materials. The best materials in each of these categories are described in the following sections.

## B. COMPOSITES

Due to its breadth of coverage (over 3000 materials) and concise format (materials ranked by mechanical properties), Composites & Laminates [10] provides an excellent source for preliminary composite material selection. The ranked property data in Reference 10 were used to identify several composites as possible air-mobile shelter construction materials. The materials were selected based on their tensile, compressive, and flexural strengths.

Shear strength was not used as a material selection criterion. The

shear strengths of all unidirectional polymer-matrix composites are relatively small, and do not vary greatly from each other. Even the strongest unidirectional polymer-matrix composites have shear strengths of 20 ksi or less.

Although modulus is an important structural analysis parameter, it was not used as a material selection criterion. A composite material with a large modulus is not necessarily a good shelter construction material. Unidirectional polymer-matrix composites, loaded in the fiber direction, exhibit linear stress-strain response up to the point of tensile failure. Thus, for two materials having the same ultimate tensile strength, the strain at failure is inversely proportional to tensile modulus. If strain-energy at failure is defined as the area under the stress-strain curve up to the point of failure, the stiffer material also has a smaller strain-energy at failure.

Ideally, shelter construction materials should have high strength and large strain at failure (and consequently, a high strain-energy at failure). Such materials will be able to withstand larger live-load-induced displacements, dissipate more energy, and result in more survivable shelters.

Following the material definitions in reference 10, the candidate air-mobile shelter composite materials have been divided into six subcategories: Advanced Composites, Compounds, Laminates, Panels and Sheets, Prepregs, and Profiles and Shapes. The differences between classes are often quite subtle.

#### 1. Advanced Composites

A composite is a macroscopically homogeneous material created by the synthetic assembly of two or more materials (a selected filler or reinforcing elements, and a compatible matrix binder) to obtain specific characteristics and properties [1]. Advanced composites are strong, tough materials created by combining one or more stiff, high-strength reinforcing fibers with a compatible resin system [1]. Advanced composites can be substituted for metals in many structural applications.

Table 1 lists the strongest materials in the Advanced Composites category, based on tensile, compressive, and flexural strength. Only those materials which ranked in the top three in at least one of the three strength categories, are listed.

TABLE 1. STRONGEST ADVANCED COMPOSITES [10].

<u>Material</u>	<u>Tension</u>	<u>Strength (ksi)</u>		<u>Flexure</u>
		<u>Compression</u>		
Thornel 2500	470	250	-	
Cycom 1010	273	215	231	
NY-30GF	225	-	-	
EMI Shielding Gr LS AC 40-60	-	-	154	
NY-40GF	-	216	-	
EMI Shielding Gr AC 30-60	-	-	93	

A brief description and summary of material properties for each of the six strongest advanced composite materials is given in Table A-1. (See Appendix A - Material Properties of Selected Composites.)

All the material strength data presented in this report were obtained from static loading conditions. Engineering reference books and manufacturers' literature do not usually contain data for dynamic loading; they rarely, if ever, contain data relevant to the exceptionally high strain rates typical of weapon loadings. However, since the goal of this report is simply to gather enough material property data to be able to screen materials for air-mobile structure construction, static data should suffice. In addition, some evidence suggests that composite material properties are not greatly affected by strain rate. After extensive dynamic testing of shelter core materials, Kuhbander and Caldwell [17] concluded that, "there is relatively little effect on honeycomb core shear strength due to test speed." Based on impact testing of composite panels, Krinke, Barber, and Nicholas [18] observed that, "A general trend of bending strength increasing with strain rate exists for most of the data but the magnitude appears small." In any case, once candidate structural materials are identified, strain rate issues can be addressed, and dynamic testing can be performed.

## 2. Compounds

Compounds are the intimate admixture of a polymer with other ingredients, such as fillers, softeners, plasticizers, reinforcement, catalysts, pigments, or dyes [6]. A thermoset compound usually contains all the ingredients necessary for the finished product, while a thermoplastic compound may require addition of pigments, blowing agents, and so forth.

Compounds come in a wide range of forms to meet specific processing requirements. The two most popular compounds are Bulk Molding Compound (BMC) and Sheet Molding Compound (SMC).

Bulk Molding Compound is a thermosetting resin, mixed with stranded reinforcement, fillers, etc., in the form of a viscous compound suitable for use in injection or compression molding [1].

Sheet Molding Compound is a composite of glass fibers, polyester resins, and pigments, fillers, and other additives, which have been compounded and processed into sheet form to facilitate handling in the molding operation [1].

Table 2 lists the strongest materials in the Compounds category, based on tensile, compressive, and flexural strength. As before, only those materials which ranked in the top three in at least one of the three strength categories are listed.

TABLE 2. STRONGEST COMPOUNDS [10].

<u>Material</u>	<u>Tension</u>	Strength (ksi)		<u>Flexure</u>
		<u>Compression</u>		
E 261H	35	42		85
RTP 287 TFE 10	33	-		-
E 21718 x 61	32	44		58
E 260H	-	42		68

A brief description and summary of material properties for each of the four strongest compounds are given in Table A-2.

Table 3 lists the strongest materials in the Bulk Molding Compounds category, based on tensile, compressive, and flexural strength. The materials listed in Table 3 are not the highest ranking according to reference 10. The top BMCs listed in Reference 10 are a family of materials manufactured by Premix, Inc., designated Premi-Glas. The listed strengths were so large, however, that they were judged to be incorrect. Reference 19, Engineering Plastics & Composites, verified that the values were, indeed, incorrect.

TABLE 3. STRONGEST BULK MOLDING COMPOUNDS [10].

<u>Material</u>	<u>Tension</u>	Strength (ksi)		<u>Flexure</u>
		<u>Compression</u>		
Polytron E-106	14	-		28
Polystruc M-106	14	28		28
Polycor C-106	14	30		28
Silryn S-106	-	29		-

A brief description and summary of material properties for each of the four strongest BMCs are given in Table A-3.

Table 4 lists the strongest materials in the Sheet Molding Compounds category, based on tensile, compressive, and flexural strength. As with the BMCs, the SMCs listed in Table 4 are not the highest ranking according to reference 10. The top SMCs listed in Reference 10 are all Premi-Glas materials. As before, the Premi-Glas data are known to be erroneous [19].

TABLE 4. STRONGEST SHEET MOLDING COMPOUNDS [10].

<u>Material</u>	<u>Tension</u>	<u>Strength (ksi)</u>		<u>Flexure</u>
		<u>Compression</u>		
Lytex 4105	140	-		185
8057	75	-		-
8068	62	-		103
VE 49595	-	42		-
Polytron E-206	-	32		-
Silryn S-206	-	32		-
Flomat 5580	-	-		112

A brief description and summary of material properties for each of the seven strongest SMCs are given in Table A-4.

### 3. Laminates

A laminate is a sheet of material made of several different bonded layers [10]. One or more of the bonded layers is itself often a composite.

Table 5 lists the strongest materials in the Laminates category, based on tensile, compressive, and flexural strength.

TABLE 5. STRONGEST LAMINATES [10].

<u>Material</u>	<u>Tension</u>	<u>Strength (ksi)</u>		<u>Flexure</u>
		<u>Compression</u>		
Cycom 985-1 GT-2148	240	200		250
Cycom 985-1 GF 6135H5	120	-		-
Gillfab 1086	110	-		-
Cycom 1827 GT 6150	-	225		310
Cycom 3100 + T300	-	167		242

A brief description and summary of material properties for each of the five strongest Laminates are given in Table A-5.

### 4. Panels & Sheets

Panels and Sheets are flat formed, finished products, similar in construction to composites [10].

Table 6 lists the strongest materials in the Panels category, based on tensile, compressive, and flexural strength. Note that only one material had a listed compressive strength.

TABLE 6. STRONGEST PANELS [10].

<u>Material</u>	<u>Tension</u>	<u>Strength (ksi)</u>		<u>Flexure</u>
		<u>Compression</u>		
Tred-Safe	32	-		39
Fire Snuf 25A 1230	15	-		-
Fire Snuf 25A 820	15	-		-
Dion FR 6131	-	26		29
Filon Standard	-	-		28

A brief description and summary of material properties for each of the five strongest Panels are given in Table A-6.

Table 7 lists the strongest materials in the Sheets category, based on tensile, compressive, and flexural strength. Reference 10 lists Extren 625 as the sheet material with the greatest compressive strength. However, these data are known to be erroneous [20], and as a result, Extren 625 is omitted from Table 7.

TABLE 7. STRONGEST SHEETS [10].

<u>Material</u>	<u>Tension</u>	<u>Strength (ksi)</u>		<u>Flexure</u>
		<u>Compression</u>		
Lamitex G215	60	70		55
Ryertex G-10	55	-		-
Ryertex G-11	50	-		-
Lamitex Grade G-5	-	70		-
Lamitex Grade G-9	-	70		55
Lamitex T6G91	-	-		63

A brief description and summary of material properties for each of the six strongest Sheets are given in Table A-7.

## 5. Prepregs

A Prepreg (preimpregnated material) is a partially processed combination of a resin and a reinforcing material, which can be used to make a composite [10].

Table 8 lists the strongest materials in the Prepregs category, based on tensile, compressive, and flexural strength.

A brief description and summary of material properties for each of the eight strongest Prepregs are given in Table A-8.

TABLE 8. STRONGEST PREPREGS [10].

<u>Material</u>	<u>Tension</u>	<u>Strength (ksi)</u>		<u>Flexure</u>
		<u>Compression</u>		
Hexcel F584/T5A190	445	-		-
Hexcel F584/T5A145	414	-		-
Hexcel F584/T4A145	404	-		-
AVCO 5505/4 - BORON	-	425		297
AVCO 5521/4 - BORON	-	425		-
Hexcel F584/T8A145	-	278		-
FX 91C34	-	-		310
Fortafil 3(C)	-	-		300

## 6. Profiles & Shapes

Profiles and Shapes are finished products [10]. They are not necessarily reinforced, and are often molded.

Table 9 lists the strongest materials in the Profiles and Shapes category, based on tensile, compressive, and flexural strength.

TABLE 9. STRONGEST PROFILES AND SHAPES [10].

<u>Material</u>	<u>Tension</u>	<u>Strength (ksi)</u>		<u>Flexure</u>
		<u>Compression</u>		
Bridon SM	214	-		-
N-S Pultruded Composites	200	-		-
Pultruded Bar Stock	110	-		-
Vespel SP-22 "S"	-	475		-
Polypenco Ultem 1000	-	420		-
Vespel SP-1 "S"	-	350		-
Vespel SP-21 "S"	-	350		-
HYR	-	-		120
ETR-FR-C-P	-	-		100
HST-II-P	-	-		100

A brief description and summary of material properties for each of the ten strongest Panels and Sheets are given in Table A-9.

## C. CORES

Current Air Force, air-transportable, tactical shelters are made with wall, floor, and roof panels of sandwich construction [17]. These sandwich panels typically consist of aluminum faces, adhesively bonded to a resin-impregnated, paper honeycomb core. Floor panels requiring high impact resistance often employ end-grain balsa wood as a core material.



Sandwich construction is common in nature. The human skull is a prime example of natural sandwich construction. The skull consists of a cellular core, laminated between solid inner and outer shells [21]. This geometry maximizes strength and stiffness, while minimizing weight.

Lightweight fillers are routinely laminated between strong facing sheets to produce strong, stiff, lightweight structural panels. Balsa wood and rigid structural foams are frequently employed as sandwich core materials. Reference 21 contains an entire chapter (Chapter 9: "The Design of Sandwich Panels with Foam Cores") devoted to the optimum design of foam-filled sandwich panels, subject to strength, stiffness, and weight constraints.

The highest strength-to-weight and stiffness-to-weight ratio sandwich panels constructed to date have utilized honeycomb cores. Honeycomb [22] is a product consisting of very thin sheets attached in such a manner as to form connecting cells. It closely resembles the honeycomb made by bees. Honeycomb can be manufactured from virtually any thin-sheet material. Common metallic-core materials are aluminum, corrosion-resistant steel, titanium, and nickel-based alloys. The most common nonmetallic core materials are Nomex, fiberglass, and kraft paper. Non-metallic core is normally dipped in liquid phenolic, polyester, or polyimide resin to achieve the final density. Honeycomb has been produced from over 500 different materials, the most recent being graphite, aramid, and ceramic [22].

Standard hexagonal honeycomb, shown schematically in Figure 2, is the most common cellular honeycomb configuration [23].

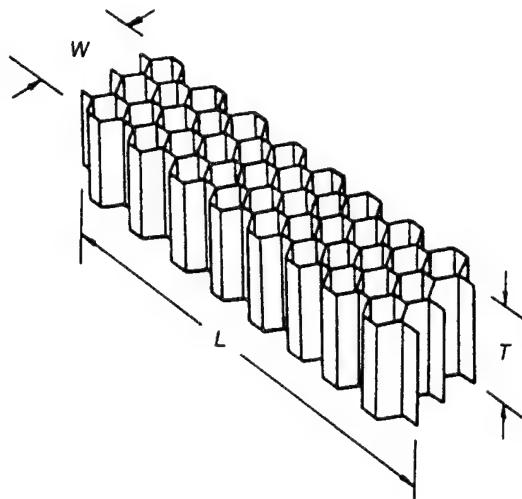


Figure 2. Hexagonal Honeycomb Geometry

As a result of the method of fabrication, hexagonal cell honeycomb is strongly orthotropic. The mechanical properties used to quantify honeycomb response are: bare compression strength, stabilized compression strength and modulus,

"L" and "W" direction (see Figure 2) shear strengths and moduli, and crush strength. In general, bare compression strength is roughly 90 percent of the stabilized strength, and crush strength is 50 percent of the stabilized strength [22]. The "L" direction shear strength and modulus values are approximately twice those in the "W" direction. Figures 3-7 present typical hexagonal honeycomb properties, as a function of density, for a variety of materials. Figure 3 shows the stabilized compressive strength of Nomex, Fiberglass, 5052 Aluminum, and 5056 Aluminum honeycomb as a function of density. Figures 4 and 5 show typical "L" and "W" direction honeycomb shear strengths as a function of density. Figures 6 and 7 show typical "L" and "W" direction honeycomb shear moduli as a function of density.

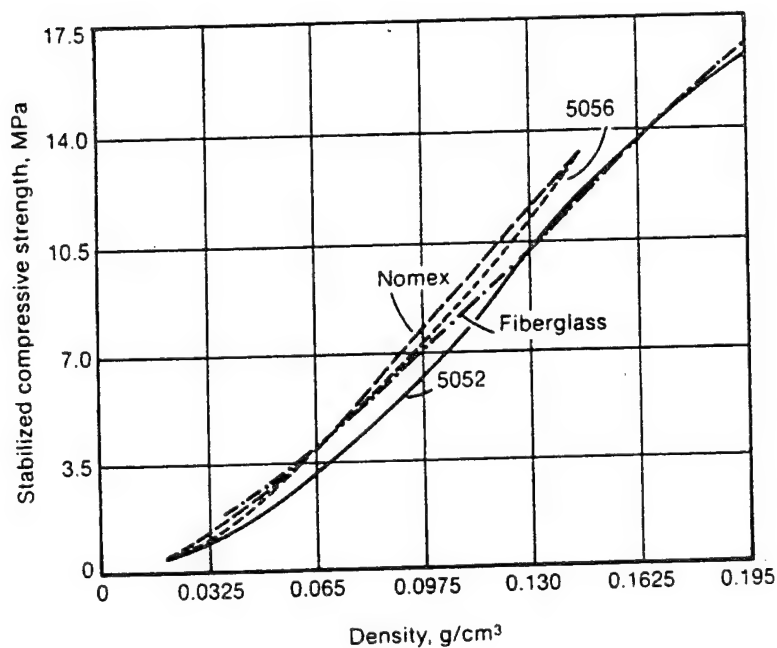


Figure 3. Typical Honeycomb Stabilized Compression Strength vs. Density [22,23].

The basic premise behind sandwich design is that the facings carry the in-plane loads, and the core carries the shear loads. Reference 24, The Basics of Bonded Sandwich Construction, offers specific guidance for designing honeycomb sandwich members. The data in Figures 4-7 indicate that grade 2024 aluminum honeycomb offers the greatest shear resistance for a given density. Since the main purpose of the sandwich core is to carry shear loads, aluminum honeycomb appears to be the core material of choice. This conclusion is confirmed by reference 25, which states, "aluminum honeycomb is a structural core material which, when bonded between high strength faces, produces a sandwich panel that has the highest strength-to-weight ratio of any structural material".

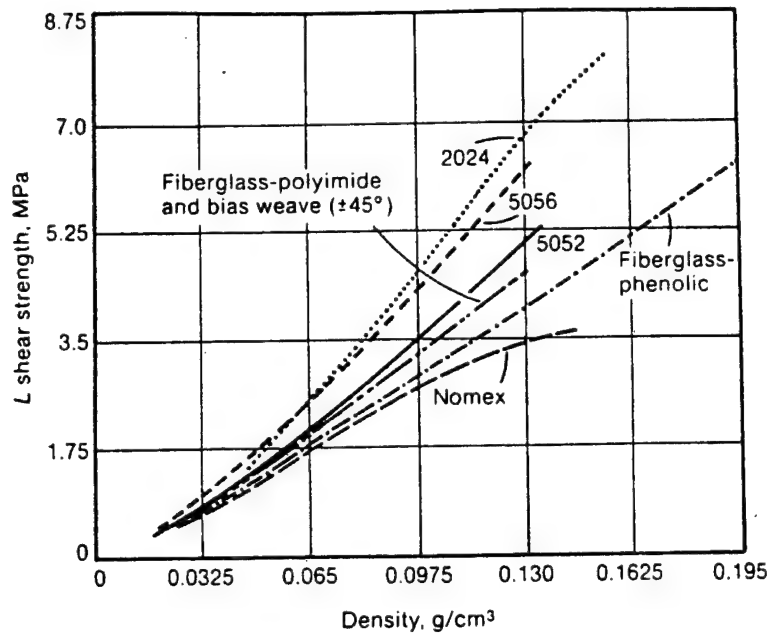


Figure 4. Typical Honeycomb "L" Shear Strength vs. Density [22,23].

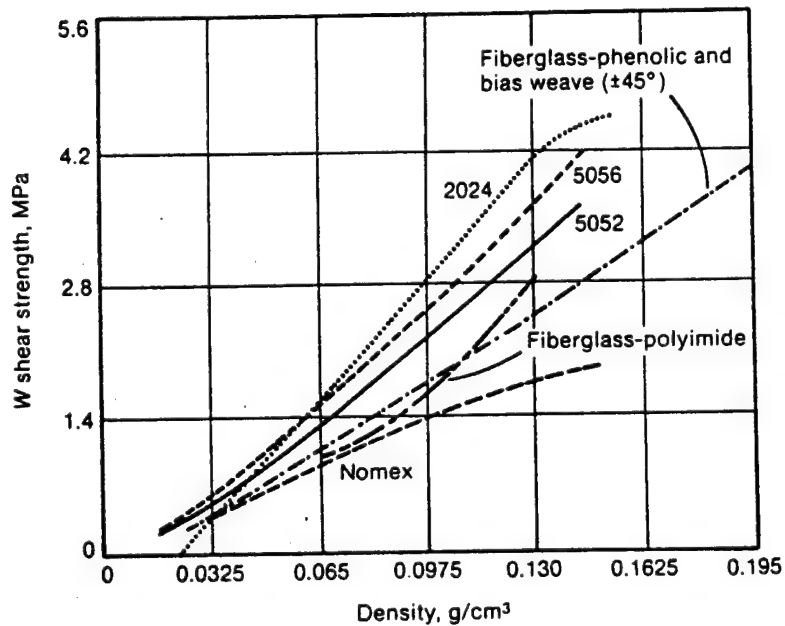


Figure 5. Typical Honeycomb "W" Shear Strength vs. Density [22,23].

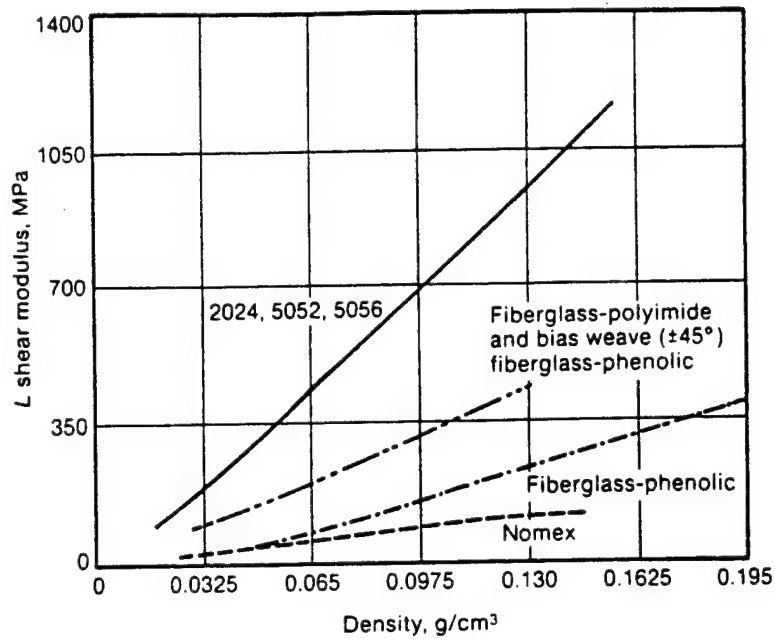


Figure 6. Typical Honeycomb "L" Shear Modulus vs. Density [22,23].

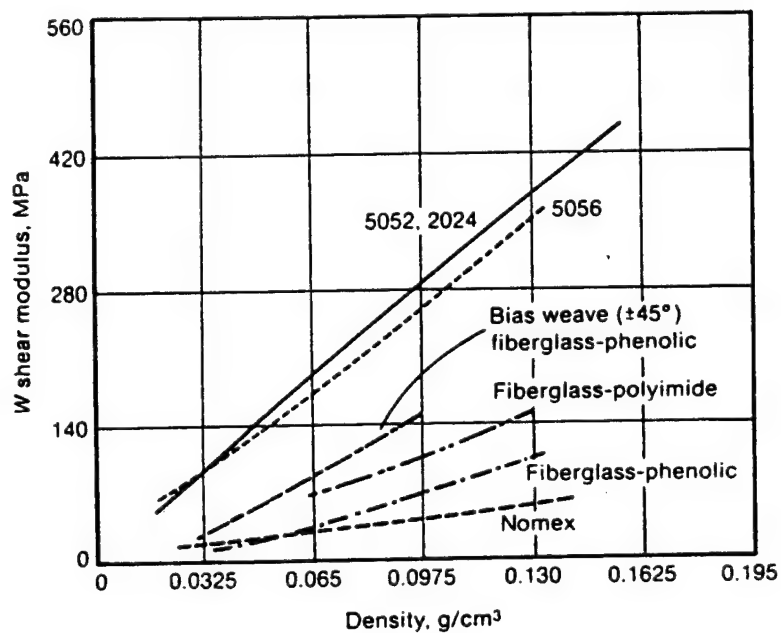


Figure 7. Typical Honeycomb "W" Shear Modulus vs. Density [22,23].

If future air-mobile shelter concepts utilize sandwich construction, Military Grade hexagonal aluminum honeycomb is recommended as a core material. Hexcel and American Cyanamid are two producers of Military Grade aluminum honeycomb (Hexcel refers to their product as "Specification Grade"). Quantitative mechanical properties of several densities of aluminum honeycomb are given in references 23 and 25. Typical properties for Hexcel, Specification Grade 2024 hexagonal aluminum honeycomb, are given in Appendix B.

#### D. ADHESIVES

There are 12 main family groups of adhesives. These 12 main groups are divided into a multitude of subgroups containing innumerable individual formulations. Reference 12 lists over 3000 commercially available adhesives. The large number of available adhesives often makes the selection process quite difficult. However, when ultimate adhesive performance is required, adhesive selection is much simpler. Lees [26] recommends that toughened epoxies be used whenever maximum performance is demanded from either a mechanical or structural assembly. They possess excellent strength, impact resistance, and durability. Toughened epoxies currently offer the best adhesive performance.

Several factors must be considered when selecting adhesives for shelter construction. Obvious considerations are the loads and the environmental conditions to which the adhesive will be subjected. The adhesive must also be chemically compatible with the substrate materials. In addition, the adhesive cure conditions must be compatible with the materials being bonded.

Shelter components will be fabricated in a factory. Shelter erection will obviously be performed in the field. Since autoclaves will not be available in the field, field bonding applications will require different adhesives than those used in the factory.

##### 1. Factory Bonding

Toughened epoxy film adhesives are recommended for factory fabrication. Film adhesives are extensively used in the aircraft industry. Film adhesives are easy to handle and place, and the toughened epoxy films are among the strongest adhesives available. However, since film adhesives require cold storage, as well as elevated temperature and pressure cure conditions, they are not appropriate for field use.

Two candidate adhesives for factory bonding are Metlbond 1137-1, manufactured by Narmco Materials, and FM 73, by American Cyanamid. Both are toughened epoxy film adhesives; are compatible with metal and composite substrates; and require an elevated temperature and pressure cure cycle (typically 1 hour at 250 degrees F and 40 psi). In the 0.030 psf weight, Metlbond 1137-1 has a lap shear strength of 7500 psi [12], and FM 73 has a lap shear strength of 6200 psi [27]. American Cyanamid [27] recommends FM 73 adhesive for use with its Cycom advanced composite materials. Recall (see Table 1) that Cycom 1010 is one of the strongest available composites.

## 2. Field Bonding

Since elevated temperature and pressure curing are not possible in the field, a two-part epoxy adhesive with room temperature cure is recommended for field construction. The first component is the epoxy, and the second component is the hardener. Two-part systems do not require refrigeration, and the separate components have an indefinite storage life [12]. After curing at room temperature, they are rigid and tough.

Scotch-Weld 2216 B/A, manufactured by the 3M Company, is a candidate adhesive for field construction. This two-part epoxy adhesive is compatible with metal, wood, plastic, and stone substrates. After curing for 7 days at 77 degrees F, it develops a lap shear strength of 4900 psi [12].

## E. BALLISTIC MATERIALS

Selecting materials for ballistic protection is not simple. To date, no direct correlation between a material's physical or mechanical properties (including impact strength), and its potential for ballistic protection, has been determined [15]. In addition, materials are not usually subjected to ballistic testing, unless they are being expressly evaluated for a particular ballistic protective capability.

There are three primary materials currently used in lightweight ballistic applications. They are S-2 Glass fibers, manufactured by Owens-Corning; Kevlar fibers, by Dupont; and Spectra fibers, by Allied Fibers. For ballistic protection applications, the fibers are woven into a tight mesh or fabric. One layer of fabric provides virtually no ballistic protection. Numerous layers must be stacked in order to develop significant ballistic resistance. Typical applications require between 10 and 50 layers [28].

Fabrics can be used for both hard and soft armor applications. In soft armor, the layers stand on their own, acting as the sole source of ballistic protection. In hard armor applications, the fabric layers are embedded in a thermoplastic, phenolic, or epoxy matrix. In general, soft armor performs better (weighs less) for low-level threats, while hard armor is better for more severe threats [28].

A lightweight hard armor study was recently conducted by Frank, et. al. at Battelle Memorial Institute [28]. The ballistic threat for this study was a 7.62-mm, full metal-jacketed bullet, with a nominal mass of 9.7 grams (150 grains), impacting at a velocity of 2750 ft/sec. The results of the study are shown in Table 10. Note that all the materials are competitively priced for the same level of protection. However, Spectra fiber clearly has the weight advantage, being lower by a factor of two. It would appear that Spectra is the best material for this threat.

TABLE 10. COMPARISON OF BALLISTIC FIBERS FOR HARD ARMOR [28].

<u>Fiber</u>	<u>Aerial Density (lb/ft<sup>2</sup>)</u>	<u>Aerial Cost (\$/ft<sup>2</sup>)</u>
Spectra	4.5	202.50
Kevlar 49	9.0	180 - 360
S-2 Glass	9.5	237.50

A similar lightweight armor study was conducted by Bless, et. al. at the University of Dayton Research Institute [29]. The threat for this study was a 60-grain, fragment-simulating projectile (FSP). It was found that Spectra, Kevlar, and S-2 Glass reinforced plastics can all defeat the 60-grain FSP at the threat velocity. However, only the Spectra-reinforced plastic can withstand the threat, while still meeting the weight constraint of 2 psf.

Based on the results of the lightweight armor studies described in references 28 and 29, it appears that Spectra fiber-reinforced plastic currently offers the greatest ballistic protection at the minimum weight.

The fact that the United States Army has recently developed a new lightweight helmet constructed of Spectra-900 fiber [30] is further conformation of Spectra's superior ballistic performance.

## SECTION IV

### SUMMARY AND CONCLUSIONS

#### A. SUMMARY

A number of commercially available, potential air-mobile, protective shelter construction materials have been identified and divided into four main categories: Composites, Cores, Adhesives, and Ballistic Materials. The best materials in each category are described herein, and a brief summary of each material's engineering properties presented. The manufacturer of every material is identified.

#### B. CONCLUSIONS

Modern materials offer the opportunity to quickly improve present shelter designs, as well as develop new shelter concepts.

##### 1. Present Shelters

Present air-mobile tactical shelters are typically constructed from sandwich panels, consisting of 1-mm thick aluminum skins bonded to a 2-inch thick, resin-impregnated, paper honeycomb core. These shelters provide very little protection from weapon effects or small arms fire. Small arms protection must be provided by covering the shelter with a ballistic resistant material.

Better core and facing materials offer a quick improvement to current tactical shelter designs. In fact, future Army tactical shelters are being developed with composite materials in mind [30]. The aluminum skins employed by current shelters will be replaced by graphite/epoxy panels. The graphite/epoxy skins will reduce shelter weight, improve ballistic protection, and increase electromagnetic shielding [30].

It is unclear from Reference 30 whether the core material will be improved as well. Using aluminum honeycomb, in combination with graphite/epoxy faces, would result in sandwich panels having significant strength and stiffness. In addition, the aluminum honeycomb core would further increase the shielding properties of the panels. Reference 23 recommends aluminum honeycomb as an RF shielding material.

##### 2. Future Designs

Future air-mobile shelter designs should exploit the impressive properties of modern engineering materials. The best shelter concepts will most likely involve a combination of materials, coupled with an innovative structural geometry. The geometry should exploit the strengths of each particular material.



## SECTION V

### REFERENCES

1. Weeton, J.W., Peters, D.M., and Thomas, K.L., Engineers' Guide to Composite Materials, American Society for Metals, Metals Park, OH, 1987.
2. Watt, W., and Perov, B.V., (Editors), Handbook of Composites - Volume 1: Strong Fibres, Elsevier Science Publishing Company, Inc., New York, NY, 1985.
3. Herakovich, C.T., and Tarnopol'skii, (Editors), Handbook of Composites - Volume 2: Structures and Design, Elsevier Science Publishing Company, Inc., New York, NY, 1989.
4. Sih, G.C., and Skudra, A.M., (Editors), Handbook of Composites - Volume 3: Failure Mechanics of Composites, Elsevier Science Publishing Company, Inc., New York, NY, 1985.
5. Kelly, A., and Mileiko, S.T., (Editors), Handbook of Composites - Volume 4: Fabrication of Composites, Elsevier Science Publishing Company, Inc., New York, NY, 1983.
6. \_\_\_\_\_, Engineered Materials Handbook - Volume 1: Composites, ASM International, Metals Park, OH, 1987.
7. \_\_\_\_\_, Engineered Materials Handbook - Volume 2: Engineering Plastics, ASM International, Metals Park, OH, 1988.
8. \_\_\_\_\_, Engineered Materials Handbook - Volume 3: Adhesives and Sealants, ASM International, Metals Park, OH, 1990.
9. \_\_\_\_\_, Engineered Materials Handbook - Volume 4: Ceramics and Glasses, ASM International, Metals Park, OH, 1991.
10. \_\_\_\_\_, Composites and Laminates / Edition 1, D.A.T.A., Inc., and the International Plastics Selector, Inc., San Diego, CA, 1987.
11. \_\_\_\_\_, Plastics / Edition 11, D.A.T.A., Inc., and the International Plastics Selector, Inc., San Diego, CA, 1990.
12. \_\_\_\_\_, Adhesives / Edition 4, D.A.T.A., Inc., and the International Plastics Selector, Inc., San Diego, CA, 1986.
13. \_\_\_\_\_, INTERNATIONAL PLASTICS SELECTOR, D.A.T.A. Business Publishing, San Diego, CA, 1990.

14. Askins, D.R., Evaluation of Materials and Technical Support for Tactical Shelters, University of Dayton Research Institute, Dayton, OH, Report AFWAL-TR-85-4070, Air Force Wright Aeronautical Laboratories, Wright-Patterson AFB, OH, June 1985.
15. Haug, F.W., Garic, G., and Pharr, M., Survey of Materials for Development of a Transportable Collective Protection System (TCPS), Computer Sciences Corporation, NSTL, MS, Air Force Aeronautical Systems Division, Wright-Patterson AFB, OH, July 1986.
16. Reinhart, T.J., and Clements, L.L., "Introduction to Composites", Engineered Materials Handbook - Volume 1: Composites, ASM International, Metals Park, OH, 1987, pp. 27-34.
17. Kuhbander, R.J., and Caldwell, S.J., Effect of Temperature, Humidity, and Loading Rate on the Shear Properties of Tactical Shelter Core Materials, University of Dayton Research Institute, Dayton, OH, Report AFWAL-TR-84-4178, Air Force Wright Aeronautical Laboratories, Wright-Patterson AFB, OH, February 1985.
18. Krinke, D.C., Barber, J.P., and Nicholas, T., The Charpy Impact Test as a Method of Evaluating Impact Resistance of Composite Materials, University of Dayton Research Institute, Dayton, OH, Technical Report AFML-TR-78-54, Air Force Materials Laboratory, Wright-Patterson AFB, OH, April 1978.
19. Bittence, J.C. (Editor), Engineering Plastics & Composites, ASM International, Materials Park, OH, 1990.
20. \_\_\_\_\_, EXTREN: Fiberglass Structural Shapes, Morrison Molded Fiberglass Company, Bristol, VA, 1990.
21. Gibson, L.J., and Ashby, M.F., Cellular Solids / Structure & Properties, Pergamon Press, Inc., Elmsford, NY, 1988.
22. Corden, J., "Honeycomb Structure," Engineered Materials Handbook - Volume 1: Composites, ASM International, Metals Park, OH, 1987, pp. 721-728.
23. \_\_\_\_\_, Mechanical Properties of Hexcel Honeycomb Materials, TSB120, Hexcel International, San Francisco, CA, 1986.
24. \_\_\_\_\_, The Basics on Bonded Sandwich Construction, TSB124, Hexcel, Dublin, CA, 1987.
25. \_\_\_\_\_, DURA-CORE: Aluminum Honeycomb Products for Aerospace and Commercial Use, American Cyanamid Company, Polymer Products Division, Wayne, NJ.
26. Lees, W.A., "Bonded Assembly - Pros, Cons and Ground Rules," Materials & Design, Vol. 11, No. 5, October 1990, pp. 227-233.
27. \_\_\_\_\_, FM 73 Film Adhesive, American Cyanamid Company, Engineered Materials Department, Havre de Grace, MD.

28. Frank, G., Moler, C., McInerney, S., Newman, D.C., Hill, T.E., Zamejc, E., and Mikalauskas, G., Collective Protection System Integration Study (CPSIS), Battelle Memorial Institute, Columbus, OH, Report AFWAL-TR-88-3092, Air Force Wright Aeronautical Laboratories, Wright-Patterson AFB, OH, 31 January 1989.
29. Bless, S.J., Rondeau, R., and Askins, D.R., Evaluation of Lightweight Armors for FSP Protection, University of Dayton Research Institute, Dayton, OH, Report WRDC-TR-89-4066, Wright Research and Development Center, Wright-Patterson AFB, OH, April 1989.
30. Crowson, A., and Mayer, G., "Army Research Activities in Advanced Composite Materials," Advanced Composites III: Expanding the Technology, ASM International, Metals Park, OH, 1987.

## SECTION VI

### BIBLIOGRAPHY

#### PROPERTIES AND MECHANICS OF ADVANCED COMPOSITE MATERIALS

- Ashbee, K.H.G., Fundamental Principles of Fiber Reinforced Composites, Technomic Publishing Company, Inc., Lancaster, PA, 1989.
- Bank, L.C., "Flexural and Shear Moduli of FRP Beams," Structural Materials, American Society of Civil Engineers, New York, NY, 1989.
- Bittence, J.C., (Editor), Engineering Plastics and Composites, ASM International, Metals Park, OH, 1990.
- Brostow, W., and Corneliussen, R.D., (Editors), Failure of Plastics, Macmillan Publishing Company, Inc., New York, NY, 1986.
- Chawla, K.K., Composite Materials / Science and Engineering, Springer-Verlag, New York, NY, 1987.
- Halpin, J.C., Primer on Composite Materials: ANALYSIS, Technomic Publishing Company, Inc., Lancaster, PA, 1984.
- Herakovich, C.T., and Tarnopol'skii, (Editors), Handbook of Composites - Volume 2: Structures and Design, Elsevier Science Publishing Company, Inc., New York, NY, 1989.
- Jackson, K.E., and Fasanella, E.L., Scaling Effects in the Static Large Deflection Response of Graphite-Epoxy Composite Beams, NASA Technical Memorandum 101619, June 1989.
- Kelly, A., and Mileiko, S.T., (Editors), Handbook of Composites - Volume 4: Fabrication of Composites, Elsevier Science Publishing Company, Inc., New York, NY, 1983.
- Krinke, D.C., Barber, J.P., and Nicholas, T., The Charpy Impact Test as a Method of Evaluating Impact Resistance of Composite Materials, University of Dayton Research Institute, Dayton, OH, Technical Report AFML-TR-78-54, Air Force Materials Laboratory, Wright-Patterson AFB, OH, April 1978.
- Mallick, P.K., Fiber-Reinforced Composites / Materials, Manufacturing, and Design, Marcel Dekker, Inc., New York, NY, 1988.
- Rogers, C.A., (Editor), Smart Materials, Structures, and Mathematical Issues, Technomic Publishing Company, Inc., Lancaster, PA, 1989.

Sih, G.C., and Skudra, A.M., (Editors), Handbook of Composites - Volume 3: Failure Mechanics of Composites, Elsevier Science Publishing Company, Inc., New York, NY, 1985.

Watt, W., and Perov, B.V., (Editors), Handbook of Composites - Volume 1: Strong Fibres, Elsevier Science Publishing Company, Inc., New York, NY, 1985.

Weeton, J.W., Peters, D.M., and Thomas, K.L., Engineers' Guide to Composite Materials, American Society for Metals, Metals Park, OH, 1987.

Whitney, J.M., and McCullough, R.L., Delaware Composites Design Encyclopedia - Volume 2: Micromechanical Materials Modeling, Technomic Publishing Company, Inc., Lancaster, PA, 1990.

Zweben, C., Hahn, H.T., and Chou, T.W., Delaware Composites Design Encyclopedia - Volume 1: Mechanical Behavior and Properties of Composite Materials, Technomic Publishing Company, Inc., Lancaster, PA, 1989.

\_\_\_\_\_, Composites and Laminates / Edition 1, D.A.T.A., Inc., and The International Plastics Selector, Inc., San Diego, CA, 1987.

\_\_\_\_\_, Engineered Materials Handbook - Volume 1: Composites, ASM International, Metals Park, OH, 1987.

\_\_\_\_\_, Engineered Materials Handbook - Volume 2: Engineering Plastics, ASM International, Metals Park, OH, 1988.

\_\_\_\_\_, How to Apply Advanced Composites Technology, ASM International, Metals Park, OH, 1988.

\_\_\_\_\_, Advanced Composites / The Latest Developments, ASM International, Metals Park, OH, 1986.

\_\_\_\_\_, Advanced Composites III: Expanding the Technology, ASM International, Metals Park, OH, 1987.

#### TRANSPORTABLE SHELTER RESEARCH

Askins, D.R., Evaluation of Materials and Technical Support for Tactical Shelters, University of Dayton Research Institute, Dayton, OH, Report AFWAL-TR-85-4070, Air Force Wright Aeronautical Laboratories, Wright-Patterson AFB, OH, June 1985.

Brentjes, J., Evaluation of a Multi-Layered Honeycomb Sandwich Concept for use in Transportable Shelters, Hexcel Corporation, Dublin, CA, Report AFWAL-TR-85-4126, Air Force Wright Aeronautical Laboratory, Wright-Patterson AFB, OH, January 1986.

- Dale, J., Paul, E., and Hottman, S.B., Chemically Hardened Army Medical Facilities, System Research Laboratories, Inc., Dayton, OH, Report NATICK/TR-87/018L, U.S. Army Natick RD & E Center, Natick, MA, August 1986.
- Frank, G., Moler, C., McInerney, S., Newman, D.C., Hill, T.E., Zamejc, E., and Mikalauskas, G., Collective Protection System Integration Study (CPSIS), Battelle Memorial Institute, Columbus, OH, Report AFWAL-TR-88-3092, Air Force Wright Aeronautical Laboratory, Wright-Patterson AFB, OH, January 1989.
- Gaylor, K., Radar Absorbing Materials - Mechanisms and Materials, Report MRL-TR-89-1, DSTO Materials Research Laboratory, Victoria, Australia, February 1989.
- Haug, F.W., Garic, G., and Pharr, M., Survey of Materials for Development of a Transportable Collective Protection System (TCPS), Computer Sciences Corporation, NSTL, MS, Air Force Aeronautical Systems Division, Wright-Patterson AFB, OH, July 1986.
- Kuhbander, R.J., and Caldwell, S.J., Effect of Temperature, Humidity, and Loading Rate on the Shear Properties of Tactical Shelter Core Materials, University of Dayton Research Institute, Dayton, OH, Report AFWAL-TR-84-4178, Air Force Wright Aeronautical Laboratories, Wright-Patterson AFB, OH, February 1985.
- Sinofsky, M., and Fowler, W., Development of a Trailerless Collective Protection Shelter, CHEMFAB New York, Inc., Buffalo, NY, Report NATICK/TR-88/028L, U.S. Army Natick RD & E Center, Natick, MA, 31 July 1987.

**APPENDIX A**  
**MATERIAL PROPERTIES OF SELECTED COMPOSITES**

TABLE A-1. ADVANCED COMPOSITES - MATERIAL PROPERTIES [10].

Material: **Thorne1 2500**

Manufacturer: Amoco Performance

Description: Fiber reinforced TS (thermosetting) epoxy

Tensile Strength, psi:  $4.70 \times 10^5$

Tensile Modulus, psi:  $2.50 \times 10^6$

Compressive Strength, psi:  $2.50 \times 10^5$

Flexural Strength, psi: -----

Flexural Modulus, psi: -----

Density, lbs/ft<sup>3</sup>: -----

Material: **Cycom 1010**

Manufacturer: American Cyanamid

Description: Glass fiber reinforced TS epoxy

Tensile Strength, psi:  $2.73 \times 10^5$

Tensile Modulus, psi:  $1.90 \times 10^7$

Compressive Strength, psi:  $2.15 \times 10^5$

Flexural Strength, psi:  $2.31 \times 10^5$

Flexural Modulus, psi:  $1.85 \times 10^7$

Density, lbs/ft<sup>3</sup>: 97.4

Material: **NY-30GF**

Manufacturer: Compound Tech Inc

Description: Glass fiber reinforced TP (thermoplastic)

Polyamide-Nylon 6

Tensile Strength, psi:  $2.25 \times 10^5$

Tensile Modulus, psi:  $1.30 \times 10^6$

Compressive Strength, psi:  $2.25 \times 10^4$

Flexural Strength, psi:  $3.30 \times 10^4$

Flexural Modulus, psi:  $1.10 \times 10^6$

Density, lbs/ft<sup>3</sup>: 86.2

Material: **EMI Shielding Gr LS AC 40-60**

Manufacturer: Phillips Petroleum

Description: Carbon fiber reinforced TP Polyphenylene

Sulfide

Tensile Strength, psi:  $1.52 \times 10^5$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi:  $1.54 \times 10^5$

Flexural Modulus, psi:  $1.41 \times 10^7$

Density, lbs/ft<sup>3</sup>: -----

Material: **NY-40GF**

Manufacturer: Compound Tech Inc

Description: Glass fiber reinforced TP Polyamide-Nylon 6

Tensile Strength, psi:  $2.50 \times 10^4$

Tensile Modulus, psi:  $2.10 \times 10^6$

Compressive Strength, psi:  $2.16 \times 10^5$

Flexural Strength, psi:  $3.50 \times 10^4$

Flexural Modulus, psi:  $1.40 \times 10^6$

Density, lbs/ft<sup>3</sup>: 91.1



TABLE A-1. ADVANCED COMPOSITES - MATERIAL PROPERTIES [10].  
(Continued)

Material: EMI Shielding Gr AC 30-60  
Manufacturer: Phillips Petroleum  
Description: Carbon fiber fabric reinforced TP  
Polyphenylene Sulfide  
Tensile Strength, psi:  $7.50 \times 10^4$   
Tensile Modulus, psi: -----  
Compressive Strength, psi: -----  
Flexural Strength, psi:  $9.30 \times 10^4$   
Flexural Modulus, psi:  $6.80 \times 10^6$   
Density, lbs/ft<sup>3</sup>: -----

TABLE A-2. COMPOUNDS - MATERIAL PROPERTIES [10].

Material: E 261H

Manufacturer: Fiberite

Description: Long glass fiber reinforced TS epoxy

Tensile Strength, psi:  $3.50 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $4.20 \times 10^4$

Flexural Strength, psi:  $8.50 \times 10^4$

Flexural Modulus, psi:  $4.20 \times 10^6$

Density, lbs/ft<sup>3</sup>: 118

Material: RTP 287 TFE 10

Manufacturer: RTP Company

Description: Carbon fiber reinforced TP Polyamide-Nylon 6/6

Tensile Strength, psi:  $3.30 \times 10^4$

Tensile Modulus, psi:  $4.20 \times 10^6$

Compressive Strength, psi:  $2.40 \times 10^4$

Flexural Strength, psi:  $5.10 \times 10^4$

Flexural Modulus, psi:  $3.10 \times 10^6$

Density, lbs/ft<sup>3</sup>: 86.8

Material: E 21718 x 61

Manufacturer: Fiberite

Description: Carbon fiber reinforced TS epoxy Tensile

strength, psi:  $3.20 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $4.40 \times 10^4$

Flexural Strength, psi:  $5.80 \times 10^4$

Flexural Modulus, psi:  $8.20 \times 10^6$

Density, lbs/ft<sup>3</sup>: 94.3

Material: E 260H

Manufacturer: Fiberite

Description: Long glass fiber reinforced TS epoxy

Tensile Strength, psi:  $2.70 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $4.20 \times 10^4$

Flexural Strength, psi:  $6.80 \times 10^4$

Flexural Modulus, psi:  $4.10 \times 10^6$

Density, lbs/ft<sup>3</sup>: 118

TABLE A-3. BULK MOLDING COMPOUNDS - MATERIAL PROPERTIES [10].

Material: **Polytron E-106**

Manufacturer: Polymer Engineering

Description: Glass fiber reinforced unspecified/proprietary  
binder

Tensile Strength, psi:  $1.40 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $2.80 \times 10^4$

Flexural Strength, psi:  $2.80 \times 10^4$

Flexural Modulus, psi:  $1.70 \times 10^6$

Density, lbs/ft<sup>3</sup>: 109

Material: **Polystruc M-106**

Manufacturer: Polymer Engineering

Description: Glass fiber reinforced unspecified/proprietary  
binder

Tensile Strength, psi:  $1.40 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $2.80 \times 10^4$

Flexural Strength, psi:  $2.80 \times 10^4$

Flexural Modulus, psi:  $1.80 \times 10^6$

Density, lbs/ft<sup>3</sup>: 111

Material: **Polycor C-106**

Manufacturer: Polymer Engineering

Description: Glass fiber reinforced TS Vinyl Ester

Tensile Strength, psi:  $1.40 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $3.00 \times 10^4$

Flexural Strength, psi:  $2.80 \times 10^4$

Flexural Modulus, psi:  $1.80 \times 10^6$

Density, lbs/ft<sup>3</sup>: 112

Material: **Silryn S-106**

Manufacturer: Polymer Engineering

Description: Glass fiber reinforced TS Polyester

Tensile Strength, psi:  $1.35 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $2.90 \times 10^4$

Flexural Strength, psi:  $2.80 \times 10^4$

Flexural Modulus, psi:  $1.70 \times 10^6$

Density, lbs/ft<sup>3</sup>: 112

TABLE A-4. SHEET MOLDING COMPOUNDS - MATERIAL PROPERTIES [10].

Material: **Lytex 4105**

Manufacturer: Quantum Composites

Description: Glass fiber reinforced TS epoxy

Tensile Strength, psi:  $1.40 \times 10^5$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi:  $1.85 \times 10^5$

Flexural Modulus, psi:  $6.00 \times 10^6$

Density, lbs/ft<sup>3</sup>: 119

Material: **8057**

Manufacturer: Applied Composites

Description: Graphite fiber reinforced TS polyester

Tensile Strength, psi:  $7.50 \times 10^4$

Tensile Modulus, psi:  $1.25 \times 10^7$

Compressive Strength, psi:  $2.99 \times 10^4$

Flexural Strength, psi:  $9.60 \times 10^4$

Flexural Modulus, psi:  $8.00 \times 10^6$

Density, lbs/ft<sup>3</sup>: 105

Material: **8068**

Manufacturer: Applied Composites

Description: Graphite fiber reinforced TS polyester

Tensile Strength, psi:  $6.20 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi:  $1.03 \times 10^5$

Flexural Modulus, psi:  $5.00 \times 10^6$

Density, lbs/ft<sup>3</sup>: 114

Material: **VE 49595**

Manufacturer: Fiberite

Description: Glass fiber reinforced TS Vinyl Ester

Tensile Strength, psi:  $3.90 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $4.20 \times 10^4$

Flexural Strength, psi:  $7.00 \times 10^4$

Flexural Modulus, psi:  $2.80 \times 10^6$

Density, lbs/ft<sup>3</sup>: 117

Material: **Silryn S-206**

Manufacturer: Polymer Engineering

Description: Glass fiber reinforced TS Polyester

Tensile Strength, psi:  $1.60 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $3.20 \times 10^4$

Flexural Strength, psi:  $3.20 \times 10^4$

Flexural Modulus, psi:  $1.90 \times 10^6$

Density, lbs/ft<sup>3</sup>: 109

TABLE A-4. SHEET MOLDING COMPOUNDS - MATERIAL PROPERTIES [10].  
(Continued)

Material: **Polytron E-206**

Manufacturer: Polymer Engineering

Description: Glass fiber reinforced unspecified/proprietary  
binder

Tensile Strength, psi:  $1.60 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $3.20 \times 10^4$

Flexural Strength, psi:  $3.10 \times 10^4$

Flexural Modulus, psi:  $1.90 \times 10^6$

Density, lbs/ft<sup>3</sup>: 107

Material: **Flomat 5580**

Manufacturer: Freeman Chemicals

Description: Glass fiber reinforced TS Polyester Tensile

Strength, psi:  $1.00 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi:  $1.12 \times 10^5$

Flexural Modulus, psi:  $1.60 \times 10^6$

Density, lbs/ft<sup>3</sup>: 114

TABLE A-5. LAMINATES - MATERIAL PROPERTIES [10].

Material: **Cycom 985-1 GT-2148**  
 Manufacturer: American Cyanamid  
 Description: Graphite fiber reinforced TS epoxy  
 Tensile Strength, psi:  $2.40 \times 10^5$   
 Tensile Modulus, psi:  $1.95 \times 10^7$   
 Compressive Strength, psi:  $2.00 \times 10^5$   
 Flexural Strength, psi:  $2.50 \times 10^5$   
 Flexural Modulus, psi:  $1.75 \times 10^7$   
 Shear Strength, psi:  $1.70 \times 10^4$   
 Density, lbs/ft<sup>3</sup>: 97.4

Material: **Cycom 985-1 GF 6135H5**  
 Manufacturer: American Cyanamid  
 Description: Glass fiber reinforced TS epoxy  
 Tensile Strength, psi:  $1.20 \times 10^5$   
 Tensile Modulus, psi:  $1.05 \times 10^7$   
 Compressive Strength, psi:  $1.15 \times 10^5$   
 Flexural Strength, psi:  $1.65 \times 10^5$   
 Flexural Modulus, psi:  $1.00 \times 10^7$   
 Shear Strength, psi:  $1.00 \times 10^4$   
 Density, lbs/ft<sup>3</sup>: 101

Material: **Gillfab 1086**  
 Manufacturer: MC Gill Corp  
 Description: Graphite fiber reinforced TS epoxy  
 Tensile Strength, psi:  $1.10 \times 10^5$   
 Tensile Modulus, psi:  $1.18 \times 10^7$   
 Compressive Strength, psi:  $1.10 \times 10^5$   
 Flexural Strength, psi:  $1.57 \times 10^5$   
 Flexural Modulus, psi:  $1.29 \times 10^7$   
 Shear Strength, psi: -----  
 Density, lbs/ft<sup>3</sup>: 98.6

Material: **Cycom 1827 GT 6150**  
 Manufacturer: American Cyanamid  
 Description: Graphite fiber reinforced TS epoxy  
 Tensile Strength, psi: -----  
 Tensile Modulus, psi: -----  
 Compressive Strength, psi:  $2.25 \times 10^5$   
 Flexural Strength, psi:  $3.10 \times 10^5$   
 Flexural Modulus, psi:  $1.83 \times 10^7$   
 Shear Strength, psi:  $1.79 \times 10^4$   
 Density, lbs/ft<sup>3</sup>: 98.0

TABLE A-5. LAMINATES - MATERIAL PROPERTIES [10].  
(Continued)

Material: Cycom 3100 + T300  
Manufacturer: American Cyanamid  
Description: Graphite fiber reinforced TS Bismaleimide  
Tensile Strength, psi:  $2.70 \times 10^4$   
Tensile Modulus, psi: -----  
Compressive Strength, psi:  $1.67 \times 10^5$   
Flexural Strength, psi:  $2.42 \times 10^5$   
Flexural Modulus, psi: -----  
Shear Strength, psi:  $1.93 \times 10^4$   
Density, lbs/ft<sup>3</sup>: -----

TABLE A-6. PANELS - MATERIAL PROPERTIES [10].

Material: **Tred-Safe**  
 Manufacturer: Resolite  
 Description: Glass fiber reinforced TP Polyester/Acrylic  
 Tensile Strength, psi:  $3.20 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi: -----  
 Flexural Strength, psi:  $3.90 \times 10^4$   
 Flexural Modulus, psi:  $1.17 \times 10^6$   
 Density, lbs/ft<sup>3</sup>: -----

Material: **Fire Snuf 25A 1230**  
 Manufacturer: Resolite  
 Description: Glass fiber reinforced TP Acrylic  
 Tensile Strength, psi:  $1.50 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi: -----  
 Flexural Strength, psi:  $1.90 \times 10^4$   
 Flexural Modulus, psi:  $7.00 \times 10^5$   
 Density, lbs/ft<sup>3</sup>: -----

Material: **Fire Snuf 25A 820**  
 Manufacturer: Resolite  
 Description: Glass fiber reinforced TP Acrylic  
 Tensile Strength, psi:  $1.50 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi: -----  
 Flexural Strength, psi:  $1.90 \times 10^4$   
 Flexural Modulus, psi:  $7.00 \times 10^5$   
 Density, lbs/ft<sup>3</sup>: -----

Material: **Dion FR 6131**  
 Manufacturer: Koppers Co, Inc  
 Description: Glass fiber reinforced TS Polyester  
 Tensile Strength, psi:  $1.38 \times 10^4$   
 Tensile Modulus, psi:  $4.50 \times 10^5$   
 Compressive Strength, psi:  $2.69 \times 10^4$   
 Flexural Strength, psi:  $2.94 \times 10^4$   
 Flexural Modulus, psi:  $1.00 \times 10^6$   
 Density, lbs/ft<sup>3</sup>: -----

Material: **Filon Standard**  
 Manufacturer: Filon  
 Description: Glass fiber reinforced TP Polyester/Acrylic  
 Tensile Strength, psi:  $1.09 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi: -----  
 Flexural Strength, psi:  $2.82 \times 10^4$   
 Flexural Modulus, psi:  $1.10 \times 10^6$   
 Density, lbs/ft<sup>3</sup>: -----



TABLE A-7. SHEETS - MATERIAL PROPERTIES [10].

Material: **Lamitex G215**  
 Manufacturer: Franklin Fibre  
 Description: Glass fiber reinforced TS epoxy  
 Tensile Strength, psi:  $6.00 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi:  $7.00 \times 10^4$   
 Flexural Strength, psi:  $5.50 \times 10^4$   
 Flexural Modulus, psi:  $2.50 \times 10^6$   
 Density, lbs/ft<sup>3</sup>: 109

Material: **Ryertex G-10**  
 Manufacturer: Ryerson  
 Description: Glass fabric reinforced TS epoxy  
 Tensile Strength, psi:  $5.50 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi:  $6.50 \times 10^4$   
 Flexural Strength, psi: -----  
 Flexural Modulus, psi: -----  
 Density, lbs/ft<sup>3</sup>: -----

Material: **Ryertex G-11**  
 Manufacturer: Ryerson  
 Description: Glass fabric reinforced TS epoxy  
 Tensile Strength, psi:  $5.00 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi:  $6.00 \times 10^4$   
 Flexural Strength, psi: -----  
 Flexural Modulus, psi: -----  
 Density, lbs/ft<sup>3</sup>: -----

Material: **Lamitex Grade G-5**  
 Manufacturer: Franklin Fibre  
 Description: Glass fabric reinforced TS Melamine  
 Tensile Strength, psi:  $3.70 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi:  $7.00 \times 10^4$   
 Flexural Strength, psi:  $4.40 \times 10^4$   
 Flexural Modulus, psi:  $1.70 \times 10^6$   
 Density, lbs/ft<sup>3</sup>: 119

Material: **Lamitex Grade G-9**  
 Manufacturer: Franklin Fibre  
 Description: Glass fabric reinforced TS Melamine  
 Tensile Strength, psi:  $3.70 \times 10^4$   
 Tensile Modulus, psi: -----  
 Compressive Strength, psi:  $7.00 \times 10^4$   
 Flexural Strength, psi:  $5.50 \times 10^4$   
 Flexural Modulus, psi:  $2.50 \times 10^6$   
 Density, lbs/ft<sup>3</sup>: 119

TABLE A-7. SHEETS - MATERIAL PROPERTIES [10].  
(Continued)

Material: Lamitex T6G91  
Manufacturer: Franklin Fibre  
Description: Glass fabric reinforced TS Polyimide  
Tensile Strength, psi: -----  
Tensile Modulus, psi: -----  
Compressive Strength, psi:  $5.80 \times 10^4$   
Flexural Strength, psi:  $6.35 \times 10^4$   
Flexural Modulus, psi:  $5.00 \times 10^6$   
Density, lbs/ft<sup>3</sup>: 119

TABLE A-8. PREPREGS - MATERIAL PROPERTIES [10].

**Material: Hexcel F584/T5A190**

**Manufacturer: Hexcel**

**Description: Carbon Tape reinforced TS epoxy**

**Tensile Strength, psi:  $4.45 \times 10^5$**

**Tensile Modulus, psi:  $2.68 \times 10^7$**

**Compressive Strength, psi:  $2.74 \times 10^5$**

**Flexural Strength, psi: -----**

**Flexural Modulus, psi: -----**

**Density, lbs/ft<sup>3</sup>: -----**

**Material: Hexcel F584/T5A145**

**Manufacturer: Hexcel**

**Description: Carbon Tape reinforced TS epoxy**

**Tensile Strength, psi:  $4.14 \times 10^5$**

**Tensile Modulus, psi:  $2.59 \times 10^7$**

**Compressive Strength, psi:  $2.51 \times 10^5$**

**Flexural Strength, psi:  $2.65 \times 10^5$**

**Flexural Modulus, psi:  $2.24 \times 10^7$**

**Density, lbs/ft<sup>3</sup>: -----**

**Material: Hexcel F584/T4A145**

**Manufacturer: Hexcel**

**Description: Carbon Tape reinforced TS epoxy**

**Tensile Strength, psi:  $4.04 \times 10^5$**

**Tensile Modulus, psi:  $2.19 \times 10^7$**

**Compressive Strength, psi:  $2.69 \times 10^5$**

**Flexural Strength, psi:  $2.85 \times 10^5$**

**Flexural Modulus, psi:  $2.05 \times 10^7$**

**Density, lbs/ft<sup>3</sup>: -----**

**Material: AVCO 5505/4 - BORON**

**Manufacturer: Avco Specialty**

**Description: Boron Filament reinforced TS epoxy**

**Tensile Strength, psi:  $2.46 \times 10^5$**

**Tensile Modulus, psi:  $3.04 \times 10^7$**

**Compressive Strength, psi:  $4.25 \times 10^5$**

**Flexural Strength, psi:  $2.97 \times 10^5$**

**Flexural Modulus, psi:  $2.75 \times 10^7$**

**Density, lbs/ft<sup>3</sup>: 125**

**Material: AVCO 5521/4 - BORON**

**Manufacturer: Avco Specialty**

**Description: Boron Filament reinforced TS epoxy**

**Tensile Strength, psi:  $2.20 \times 10^5$**

**Tensile Modulus, psi:  $3.04 \times 10^7$**

**Compressive Strength, psi:  $4.25 \times 10^5$**

**Flexural Strength, psi:  $2.59 \times 10^5$**

**Flexural Modulus, psi:  $2.75 \times 10^7$**

**Density, lbs/ft<sup>3</sup>: 125**

TABLE A-8. PREPREGS - MATERIAL PROPERTIES [10].  
(Continued)

Material: Hexcel F584/T8A145

Manufacturer: Hexcel

Description: Carbon Tape reinforced TS epoxy

Tensile Strength, psi:  $3.41 \times 10^5$

Tensile Modulus, psi:  $1.96 \times 10^7$

Compressive Strength, psi:  $2.78 \times 10^5$

Flexural Strength, psi: -----

Flexural Modulus, psi: -----

Density, lbs/ft<sup>3</sup>: -----

Material: FX 91C34

Manufacturer: Fiberite

Description: Glass Fiber reinforced TS epoxy

Tensile Strength, psi:  $1.90 \times 10^5$

Tensile Modulus, psi:  $7.80 \times 10^6$

Compressive Strength, psi: -----

Flexural Strength, psi:  $3.10 \times 10^5$

Flexural Modulus, psi:  $9.00 \times 10^6$

Density, lbs/ft<sup>3</sup>: 127

Material: Fortafil 3(C)

Manufacturer: Fortafil Fibers

Description: Carbon Fiber reinforced TS epoxy

Tensile Strength, psi:  $2.64 \times 10^5$

Tensile Modulus, psi:  $1.90 \times 10^7$

Compressive Strength, psi: -----

Flexural Strength, psi:  $3.00 \times 10^5$

Flexural Modulus, psi:  $1.80 \times 10^7$

Density, lbs/ft<sup>3</sup>: -----

TABLE A-9. PROFILES AND SHAPES - MATERIAL PROPERTIES [10].

**Material: Bridon SM**

Manufacturer: Bridon Composites

Description: Glass fiber reinforced TS polyester Tensile

Strength, psi:  $2.14 \times 10^5$

Tensile Modulus, psi:  $6.96 \times 10^6$

Compressive Strength, psi: -----

Flexural Strength, psi:  $2.61 \times 10^5$

Flexural Modulus, psi:  $6.63 \times 10^6$

Density, lbs/ft<sup>3</sup>: 125

**Material: N-S Pultruded Composites**

Manufacturer: National-Standard

Description: E-Glass, S2 Glass & Kevlar fiber reinforced  
unspecified/proprietary matrix

Tensile Strength, psi:  $2.00 \times 10^5$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi: -----

Flexural Modulus, psi: -----

Density, lbs/ft<sup>3</sup>: 124

**Material: Pultruded Bar Stock**

Manufacturer: Polygon Company

Description: Glass fiber reinforced unspecified/proprietary  
matrix

Tensile Strength, psi:  $1.10 \times 10^5$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi: -----

Flexural Modulus, psi:  $5.50 \times 10^6$

Density, lbs/ft<sup>3</sup>: 124

**Material: Vespel SP-22 "S"**

Manufacturer: EI DuPont

Description: Graphite reinforced TS polyimide

Tensile Strength, psi:  $7.50 \times 10^3$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $4.75 \times 10^5$

Flexural Strength, psi:  $1.40 \times 10^4$

Flexural Modulus, psi:  $7.00 \times 10^5$

Density, lbs/ft<sup>3</sup>: 103

**Material: Polypenco Ultem 1000**

Manufacturer: The Polymer Corp

Description: TP polyetherimide

Tensile Strength, psi: -----

Tensile Modulus, psi:  $4.30 \times 10^5$

Compressive Strength, psi:  $4.20 \times 10^5$

Flexural Strength, psi:  $2.10 \times 10^4$

Flexural Modulus, psi:  $4.80 \times 10^5$

Density, lbs/ft<sup>3</sup>: 79.3

TABLE A-8. PROFILES AND SHAPES - MATERIAL PROPERTIES [10].  
(Continued)

Material: **Vespel SP-1 "S"**

Manufacturer: EI DuPont

Description: TS polyimide

Tensile Strength, psi:  $1.25 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $3.50 \times 10^5$

Flexural Strength, psi:  $1.90 \times 10^4$

Flexural Modulus, psi:  $4.50 \times 10^5$

Density, lbs/ft<sup>3</sup>: 89.3

Material: **Vespel SP-21 "S"**

Manufacturer: EI DuPont

Description: Graphite Fiber reinforced TS polyimide

Tensile Strength, psi:  $9.50 \times 10^3$

Tensile Modulus, psi: -----

Compressive Strength, psi:  $3.50 \times 10^5$

Flexural Strength, psi:  $1.60 \times 10^4$

Flexural Modulus, psi:  $5.50 \times 10^5$

Density, lbs/ft<sup>3</sup>: 94.3

Material: **HYR**

Manufacturer: Haysite Plastics

Description: Unspecified/proprietary

Tensile Strength, psi:  $1.00 \times 10^5$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi:  $1.20 \times 10^5$

Flexural Modulus, psi: -----

Density, lbs/ft<sup>3</sup>: 117

Material: **ETR-FR-C-P**

Manufacturer: Haysite Plastics

Description: Unspecified/proprietary

Tensile Strength, psi:  $3.50 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi:  $1.00 \times 10^5$

Flexural Modulus, psi: -----

Density, lbs/ft<sup>3</sup>: 114

Material: **HST-II-P**

Manufacturer: Haysite Plastics

Description: Unspecified/proprietary

Tensile Strength, psi:  $4.00 \times 10^4$

Tensile Modulus, psi: -----

Compressive Strength, psi: -----

Flexural Strength, psi:  $1.00 \times 10^5$

Flexural Modulus, psi: -----

Density, lbs/ft<sup>3</sup>: 117

**APPENDIX B**  
**PROPERTIES OF HEXAGONAL 2024 ALUMINUM HONEYCOMB**

TABLE B-1. PROPERTIES OF HEXAGONAL 2024 ALUMINUM HONEYCOMB [23].

Material: 1/8-2024-0.0015

Manufacturer: Hexcel

Density, lbs/ft<sup>3</sup>: 5.0

Stabilized Compressive Strength, psi: 840

Stabilized Compressive Modulus, ksi: 200

Crush Strength, psi: 425

"L" Direction Shear Strength, psi: 500

"L" Direction Shear Modulus, ksi: 82.0

"W" Direction Shear Strength, psi: 315

"W" Direction Shear Modulus, ksi: 33.0

Material: 1/8-2024-0.002

Manufacturer: Hexcel

Density, lbs/ft<sup>3</sup>: 6.7

Stabilized Compressive Strength, psi: 1330

Stabilized Compressive Modulus, ksi: 300

Crush Strength, psi: 640

"L" Direction Shear Strength, psi: 760

"L" Direction Shear Modulus, ksi: 118

"W" Direction Shear Strength, psi: 470

"W" Direction Shear Modulus, ksi: 45.0

Material: 1/8-2024-0.0025

Manufacturer: Hexcel

Density, lbs/ft<sup>3</sup>: 8.0

Stabilized Compressive Strength, psi: 1900

Stabilized Compressive Modulus, ksi: 380

Crush Strength, psi: 840

"L" Direction Shear Strength, psi: 960

"L" Direction Shear Modulus, ksi: 148

"W" Direction Shear Strength, psi: 590

"W" Direction Shear Modulus, ksi: 54.0

Material: 1/8-2024-0.003

Manufacturer: Hexcel

Density, lbs/ft<sup>3</sup>: 9.5

Stabilized Compressive Strength, psi: 2500

Stabilized Compressive Modulus, ksi: 480

Crush Strength, psi: 1120

"L" Direction Shear Strength, psi: 1150

"L" Direction Shear Modulus, ksi: 170

"W" Direction Shear Strength, psi: 650

"W" Direction Shear Modulus, ksi: 64.0



TABLE B-1. PROPERTIES OF HEXAGONAL 2024 ALUMINUM HONEYCOMB [23].  
(Continued)

Material: 3/16-2024-0.0015

Manufacturer: Hexcel

Density, lbs/ft<sup>3</sup>: 3.5

Stabilized Compressive Strength, psi: 500

Stabilized Compressive Modulus, ksi: 86

Crush Strength, psi: 200

"L" Direction Shear Strength, psi: 290

"L" Direction Shear Modulus, ksi: 55.0

"W" Direction Shear Strength, psi: 180

"W" Direction Shear Modulus, ksi: 23.0

Material: 1/4-2024-0.0015

Manufacturer: Hexcel

Density, lbs/ft<sup>3</sup>: 2.8

Stabilized Compressive Strength, psi: 320

Stabilized Compressive Modulus, ksi: 40

Crush Strength, psi: 110

"L" Direction Shear Strength, psi: 200

"L" Direction Shear Modulus, ksi: 42.0

"W" Direction Shear Strength, psi: 120

"W" Direction Shear Modulus, ksi: 19.0